

## Sorption Equilibrium and Kinetics of Oil from Aqueous Solution Using Banana Pseudostem Fibers

Nurul Izza Husin<sup>1+</sup>, Nor Aimi Abdul Wahab<sup>1</sup>, Norain Isa<sup>1</sup> and Rozan Boudville<sup>2</sup>

<sup>1</sup> Department of Applied Sciences, UiTM Pulau Pinang, Malaysia

<sup>2</sup> Faculty of Electrical Engineering, UiTM Pulau Pinang, Malaysia

**Abstract.** This study describes the ability of banana pseudostem fibers as an alternative adsorbent for the removal of oil from synthetic oily wastewater. A detailed batch study with respect to its adsorption equilibrium, isotherm and kinetics were carried out at ambient temperature, various initial concentration of oil and agitation time. The batch study clearly shows that banana pseudostem fibers exhibit almost 100% adsorption at lower concentration of oil. Langmuir and Freundlich adsorption model were applied to describe the experimental isotherm and isotherm constants. Equilibrium data fitted well with Freundlich model. The kinetic data were best fitted to pseudo-second-order kinetic model. The result showed that this low-cost adsorbent had a high adsorption capacity, making it suitable for the oily wastewater treatment.

**Keywords:** Adsorption equilibrium, Kinetic, Oil removal, Banana Pseudostem, Adsorbent

### 1. Introduction

Over the recent years there has been an increasing concern for environmental risk of industrial activities associated with extraction, hydrocarbons, food processing, transportations and refining. These industries have increased the threat of oil pollution to the environment and subsequently concomitant discharged into the natural environment creates major ecological problem throughout the world. The wastewater is detrimental and need to have a treatment before discharge into the environment, in line with Malaysian Environmental Quality Act 1974. Unlike the free or 'floating' oil spilled in the sea, lakes or rivers, most industrial wastewaters contain oil emulsion, which possess a real problem to treatment due to its high stability and can only be separated with the help of chemical clarification (Ahmad et al., 2005). The treatment of this waste has been addressed by several techniques such as coagulation, biosorption, adsorption, filtration, screening and many more. Among the various technique adsorption process is one of the effective methods for removing organic and inorganic pollutants in waterway system (Kumar et al., 2000). Traditionally, activated carbon (AC) was used as adsorbent for adsorption process. Due to low efficiency and high cost of activated carbon for oily wastewater treatment (Moazed and Viraraghavan, 2005), the possibility of using inexpensive materials as alternatives was explored by many researchers in the past years. Low cost adsorbent could be generated from agriculture waste because of their low-cost and widespread availability. Some examples of agro waste that have been used for the removal of oil are barley straw (Sharif Ibrahim et al., 2009), walnut shell (Srinivasan and Viraraghavan, 2008), wool fibers (Rajakovic et al., 2007), olive waste (El-Hamouz et al., 2007).

In the present study, the ability of banana pseudostem fibers as a biosorbent for the removal of oil from synthetic oily wastewater was investigated. Therefore, the purpose of this study was to assess the feasibility of banana pseudostem fibers (BP) as sorbent for the removal of oil from oily wastewater. Adsorption isotherms and kinetics of the sorption process were also discussed.

### 2. Materials and Methods

---

<sup>+</sup> Corresponding author. Tel.: +6043823357; fax: +6043822853.  
E-mail address: nurulizza.husin@ppinang.uitm.edu.my

## 2.1. Sorbent

Banana pseudostems fibers from the family of *Musa acuminata* x *balbisiana* Colla (ABB Group) cv 'Pisang Awak' were obtained locally. The collected materials were then washed repeatedly with distilled water to remove all the dirt particles. The washed materials were cut into small pieces (1–2 cm) then boiled for an hour. It were then placed in an oven at 45 °C for drying until constant weight, ground and sieved to obtain a particle size range of 300-355 µm. the newly prepared Banana pseudostems fibers powder (hereafter called BP) was used as adsorbent without any pre-treatment.

## 2.2. Adsorbate

A stock solution of synthetic oily wastewater was prepared by mixing 11.5g of the palm oil with 1000 mL of water. The mixture was then stabilized in a blender at high speed for 15–20 minutes. The resultant solution was milky white, which exhibited the character of chemically stabilized solution. It was later diluted to a desired oil concentration for adsorption test.

## 2.3. Equilibrium Studies

Batch adsorption experiment were carried out by mixing fixed amount of sorbent (1.0 g) with 100 mL synthetic oily wastewater solution at varying concentrations (20–100% v/v) and various contact time (20–120 min). Agitation speed, temperature, and particle size of adsorbent were fixed at 170 rpm, 27 °C and 300–355 micron respectively. As for the operating variables; original pH of solution was 6.8 and the volume of emulsified oil solution was set at 100 mL. Throughout the experiment, an Orbital shaker (GFL 3005) was used to agitate the samples and pH of solution was measured using a pH meter (Jenway 3505). Experiments were duplicated under the similar conditions and the mean values were used in calculations. The filtrate was analyzed for oil concentration using the oil and grease method recommended by APHA, AWWA, WPCF (1992) Standard Method of Examination of Water and Wastewater, with n-hexane being used as the oil-extraction solvent. The amount of adsorption at equilibrium,  $q_e$  (mg/g), was calculated using Eq. 1:

$$q_e = \frac{(C_0 - C_e)V}{W} \quad (1)$$

where  $C_0$  and  $C_e$  (mg/L) are the liquid-phase concentrations of oil at initial and equilibrium, respectively.  $V$  (L) is the volume of the solution and  $W$  (g) is the mass of dry sorbent used.

## 2.4. Kinetic studies

Kinetic experiments were identical to those of equilibrium tests. The aqueous samples were taken at preset time intervals and the concentrations of oil were similarly measured. The amount of sorption at time  $t$ ,  $q_t$  (mg/g), was calculated by

$$q_t = (C_0 - C_t)V / W \quad (2)$$

where  $C_t$  (mg/L) is the liquid-phase concentrations of oil at any time.

## 3. Results and Discussion

### 3.1. Effect of initial oil concentration and contact time

The study on effect of initial concentration was performed at room temperature, 27 °C while the pH and agitation rate were fixed at pH 6.8 and 170 rpm, respectively. The synthetic oily wastewater was diluted with distilled water to ratio 20%, 40%, 60% and 80%. The original concentration was presented as 100%. The adsorption data was illustrated in Fig. 1. It proves that amount of oil adsorbed increase with the increase in the concentration of oil. The uptake of oil increased from 190.0 to 685.0 mg/g with increase in the initial oil concentration from 20% to 100 %. A higher initial concentration provides an important driving force to overcome all resistances of the oil between the aqueous and solid phases, thus increasing the uptake. In addition, increasing the initial oil concentration increases the number of collisions between oil and the adsorbent, which enhances the adsorption process (Hameed et al., 2008). The effect of contact time on the

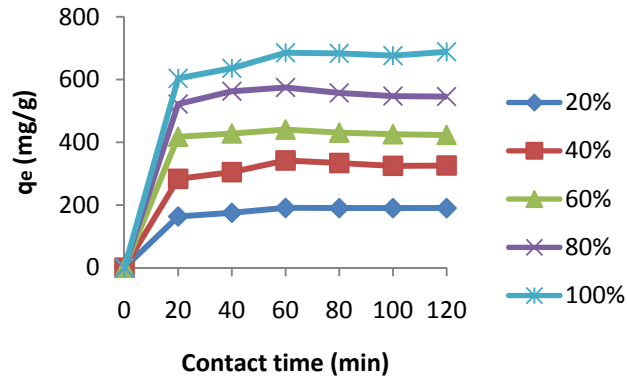


Fig. 1: Effect of contact time on removal of oil by BP at different initial concentration (dosage, 10 g/l; pH 6.8; agitation rate 170 rpm; temperature, 27 °C)

removal of oil by BP at initial concentration 20%-100% v/v showed the amount of oil adsorbed per unit mass of adsorbent increased at lower times before reaching the plateaus. According to these data, equilibrium is achieved at around 60 min. However, to be sure on the best adsorption conditions at higher concentrations levels, to obtain equilibrium at the solid/liquid interface, all the experiments were carried out with 2 h of contact time. There is no noticeable change in oil removal when the time was prolonged. The initial high rate of oil uptake may be attributed to the existence of the bare surface; however the number of available adsorption sites decreased as the number of oil adsorbed increases (Bhattacharya and Gupta, 2006).

### 3.2. Adsorption isotherms

Adsorption isotherm is the relationship between the amount of a substance adsorbed and its concentration in the equilibrium solution at constant temperature. In this study, the adsorption data were analyzed using Langmuir and Freundlich adsorption isotherm models to describe the sorption equilibrium. The applicability of the isotherm models to the adsorption study was compared by judging the correlation coefficients,  $R^2$  values.

Langmuir isotherm is based on the assumption that maximum adsorption corresponds to a saturated monolayer of solute molecules on the adsorbent surface. The linear form of Langmuir is represented as follows:

$$\frac{C_e}{q_e} = \frac{1}{Q_o b} + \frac{1}{Q_o} C_e \quad (3)$$

where  $C_e$  is the equilibrium oil concentration ( $\text{mg L}^{-1}$ ),  $q_e$  the amount of oil adsorbed per unit mass of adsorbent ( $\text{mg g}^{-1}$ ),  $Q_o$  and  $b$  is Langmuir constants related to adsorption capacity and rate of adsorption, respectively. The values of maximum adsorption capacity can be obtained from the slope of the plot of  $C_e/q_e$  versus  $C_e$  (Fig. 2). The maximum adsorption capacity of oil by BP was  $1.69\text{E}+02$  (see table 1). The correlation coefficient of Langmuir isotherm,  $R^2$  is 0.926. The essential characteristics of the Langmuir isotherm can be expressed in terms of a dimensionless constant separation factor  $R_L$  that is given in Eq. 4:

$$R_L = \frac{1}{1 + b C_o} \quad (4)$$

The value of  $R_L$  indicates the type of the isotherm to be either favorable ( $0 < R_L < 1$ ), unfavorable ( $R_L > 1$ ), linear ( $R_L = 1$ ) or irreversible ( $R_L = 0$ ). All the value of  $R_L$  lies between 0.014 and 0.065 for the initial oil concentration range from 20% to 100 % v/v. The  $R_L$  values show that favorable adsorption of oil on BP takes place. Therefore BP is favorable adsorbent.

Freundlich isotherm model is derived to model the multilayer adsorption and applicable to highly heterogeneous surface, and is given as:

$$q_e = \ln K_F + \frac{1}{n} \ln C_e \quad (5)$$

Table 1: Comparison of Langmuir and Freundlich isotherms constants for BP

Adsorbent	Langmuir			Freundlich		
	B	q <sub>o</sub>	R <sup>2</sup>	K <sub>F</sub>	N	R <sup>2</sup>
BP	7.21E-03	1.69E+02	0.926	38.29	2.880	0.976

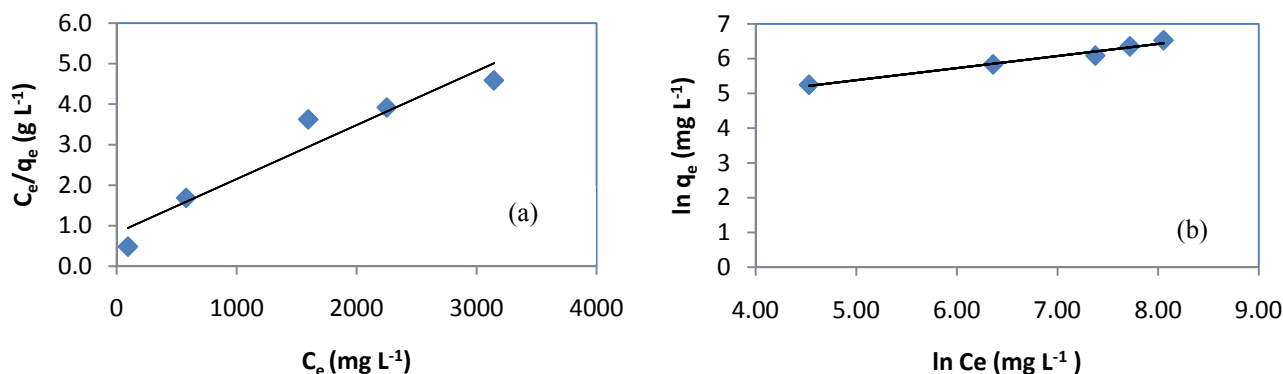


Fig. 2: Plot of (a) Langmuir isotherm, (b) Freundlich isotherm for oil sorption onto BP

where  $K_F$  and  $n$  related to adsorption capacity of adsorbent and measure of adsorption intensity, respectively. The magnitude of the exponent,  $1/n$ , gives an indication of the favorability of adsorption. Values of  $n > 1$  represent favorable adsorption condition (Ho and Mckay, 1998a). The plot of  $\ln q_e$  versus  $\ln C_e$  in Fig. 2 shows a straight line with a correlation coefficient of 0.976. The constant  $K_F$  and  $1/n$  value was determined from the plot. The value calculated was listed in table 1. The value of  $n$  determined from Freundlich isotherm was 2.88.

As seen from table 1, a high regression correlation coefficient was shown by Freundlich model. This indicates that the Freundlich model was suitable for describing the sorption equilibrium of oil by BP. Similar results were reported for oil adsorption on powder and flakes chitosan (Ahmad et al., 2005). Thus it is reasonable to conclude that the adsorption of oil on the adsorbent that consist of heterogeneous adsorption sites that are similar to each other in respect of adsorption phenomenon.

### 3.3. Kinetic studies

In order to analyze the sorption kinetics of oil on BP, two simplified kinetic model were applied to the experimental data. First, the kinetic adsorption was analyze by the Lagergren pseudo-first-order equation as depicted in Eq. 6:

$$\log(q_e - q_t) = \log q_e - \frac{k_1}{2.303} t \quad (6)$$

where  $q_e$  and  $q_t$  are the amount of oil adsorbed on adsorbent at equilibrium and time  $t$ , respectively ( $\text{mg/g}$ ), and  $k_1$  is the rate constant of first order adsorption ( $\text{min}^{-1}$ ). Value of  $k_1$  at ambient temperature were calculated from the plots of  $\log(q_e - q_t)$  versus  $t$  for different initial concentration of oil (figure not shown). The parameters of pseudo-first-order model were summarized in table 2. The set of  $R^2$  value obtained in all cases were poor and the experimental  $q_e$  value did not agree with the calculated value obtained from the linear plot. This suggests that the adsorption of oil onto BP is not a first-order reaction.

Table 2: Comparison of Langmuir and Freundlich isotherms constants for BP

Adsorbent	Initial Concentration	Pseudo-first order kinetic model				Pseudo-second order kinetic model			
		$q_e$ (exp)	$k_1$	$q_e$ (cal)	$R^2$	$k_2$	$q_e$ (cal)	$R^2$	
BP	20%	190.72	0.08	1.08	0.96	0.06	200.00	0.999	
	40%	342.20	1.02	4.68	0.69	0.04	344.80	0.995	
	60%	440.40	0.86	5.71	0.93	1.32	434.78	0.999	
	80%	574.80	0.77	11.07	0.83	0.54	555.55	0.998	
	100%	688.50	2.13	1.39	0.98	0.02	714.28	0.999	

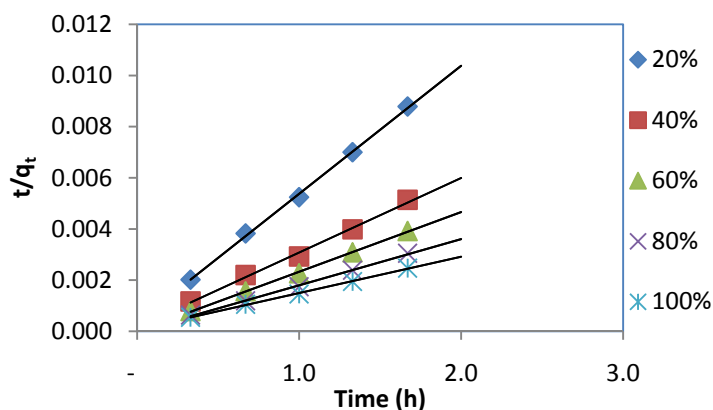


Fig. 3: Pseudo-first-order sorption kinetics of oil onto BP

While for pseudo-second-order equation based on equilibrium adsorption is expressed as Eq. 7:

$$\frac{t}{q_t} = \frac{1}{k_2 q_e^2} + \frac{1}{q_e} t \quad (7)$$

where,  $k_2$  is the pseudo-second-order rate constant of adsorption ( $\text{g mg}^{-1} \text{min}^{-1}$ ). The straight linear line in plot  $t/q_t$  vs.  $t$  (Fig. 3) proves a good agreement of experimental data with the kinetic model. The  $q_e$  and  $k_2$  values can be calculated from the slopes and intercepts of the plot respectively.

Table 2 also lists the computed results obtained for the second-order kinetic model. The correlation coefficient ( $R^2$ ) for the second-order kinetic model is almost equal to 1.0. Furthermore the calculated  $q_e$  values obtained agree very well with the  $q_e$  of the experimental data. Indicated that this model was applicable to describe the adsorption process of oil onto BP, based on assumption that the rate-limiting step maybe chemical sorption or chemisorption involving valency forces through sharing or exchange of electrons between sorbent and sorbate, provide the best correlation of data (Ho and McKay, 1999). Similar results were reported for the adsorption of oil by powder and flake chitosan (Ahmad et al., 2005).

#### 4. Conclusion

The present study demonstrated that Banana pseudostem fibers (BP), which abundantly available in Malaysia, is an efficient sorbent for the removal of oil in water and it may be an alternative to more costly adsorbents such as activated carbon. The batch studies clearly suggest that BP exhibits almost 100% adsorption at lower concentration of oil. Equilibrium data fitted well with Freundlich model, which suggests a heterogeneous coverage of oil molecules on the surface of BP. The kinetic data were best fitted to pseudo-second-order kinetic model.

#### 5. Acknowledgment

The authors are grateful to the Universiti Teknologi MARA for providing research grant and facilities for conducting the research.

## 6. References

- [1] A.L. Ahmad, S.Bhatia, N.Ibrahim, and S.Sumathi. Adsorption of residual oil from palm oil mill effluent using rubber powder. *Brazilian Journal of Chemical Engineering*, 2005. **22**(3): 371-379.
- [2] K.G.Bhattacharrya, K.G. and S.S.Gupta. Pb(II) uptake by kaolinite and montmorillonite in aqueous medium: influence of acid activation of the clays, *Colloid Surf. A: Physicochem. Eng. Asp.* 2006. **277**:191–200.
- [3] A. El-Hamouz, H.S. Hilal, N. Nassara, Z. Mardawi. Solid olive waste in environmental cleanup: Oil recovery and carbon production for water purification. *Journal of Environmental Management*. 2007. **84**:83–92
- [4] B.H. Hameed, D.K. Mahmoud, A.L. Ahmad. Equilibrium modeling and kinetic studies on the adsorption of basic dye by a low-cost adsorbent: Coconut (*Cocos nucifera*) bunch waste. *Journal of Hazardous Materials*. 2007: **158**:65-72.
- [5] Y.S. Ho and G. McKay. Sorption of dye from aqueous solution by peat. *Chem. Eng. J.* 1998. **70**:115–124.
- [6] Y.S. Ho and G. McKay. Pseudo-second order model for sorption processes. *Process Biochemistry*. 1999. **34**:451–465
- [7] S. Hokputsaa, A. Gerdditb, S. Pongsamartb, K. Inngjerdjengenc, T. Heinzed, A. Koschellad, S.E. Hardinga, P.S. Paulsen. Water-soluble polysaccharides with pharmaceutical importance from Durian rinds (*Durio zibethinus* Murr.): isolation, fractionation, characterisation and bioactivity. *Carbohydrat Polym.* 2004. **56**: 471–481.
- [8] S. Ibrahim, S.Wang, and H.M. Ang, Removal of emulsified oil from oily wastewater using agricultural waste barley straw. *Biochemical Engineering Journal* (in press).
- [9] A. Kumar, N.N. Rao and S.N. Kau. Alkali-treated straw and insoluble straw xanthate as low cost adsorbents for heavy metal removal—preparation, characterization and application. *Bioresouces Technology*. 2000. **71**:133–142.
- [10] I. Langmuir. The adsorption of gases on plane surfaces of glass, mica and platinum, *J. Am. Chem. Soc.* 1918. **40**:1361–1403.
- [11] M.H. Mas Rosemal and S. Kathiresan. The Removal of Methyl Red from Aqueous Solutions Using Banana Pseudostem Fibers, *Am. J. Applied Sci.* 2009. **6**(9): 1690-1700.
- [12] H. Moazed and T. Viraraghavan. Use of organo-clay/anthracite mixture in the separation of oil from oily waters. *Energy Sources Part A*. 2005. **27**:101–112.
- [13] K. Mohanty, M. Jha, B.C. Meikap, M.N. Biswas, M.N. Biosorption of Cr(VI) from aqueous solutions by *Eichhornia crassipes*, *Chem. Eng. J.* 2006. **117**:71–77.
- [14] S. Nanthachai. Durian: fruit development, postharvest physiology, handling and marketing in ASEAN. ASEAN Food Handling Bureau, Kuala Lumpur, Malaysia. 1999.
- [15] A.F. Pavan, C.E. Lim, S.L.P. Dias, A.C. Mazzocato. Methylene blue biosorption from aqueous solutions by yellow passion fruit waste. *Journal of Hazardous Materials*. 2008. **150**:703–712.
- [16] V. Rajakovic, G. Aleksic, M. Radetic, and L. Rajakovic. Efficiency of oil removal from real wastewater with different sorbent materials. *Journal of Hazardous Materials*. 2007. **143**: 494-499.
- [17] A. Shukla, Y.H. Zhang, P. Dubey, J.L. Margrave, S.S. Shukla. The role of sawdust in the removal of unwanted materials from water. *J. Hazard. Mater.* 2002. **95**:137–152.
- [18] A. Srinivasan and T. Viraraghavan. Oil removal from water by fungal biomass: A factorial design analysis. *Journal of Hazardous Materials*. 2010. **175**: 695-702.
- [19] A. Srinivasan and T. Viraraghavan. Removal of oil by walnut shell media. *Bioresource Technology*. 2008. **99**: 8217-8220.
- [20] S. Subhadrabandhu and S. Ketsa. Durian King of Tropical Fruit, CABI Publishing, New York. 2001.
- [21] W.S. Wan Ngah and M.A.K.M. Hanafiah. Biosorption of copper ions from dilute aqueous solutions on base treated rubber (*Hevea brasiliensis*) leaves powder: kinetics, isotherm, and biosorption mechanisms, *J. Environ. Sci.* 2008. **20**:1168–1176.
- [22] Y.B. Zhou, X.Y. Tang, X.M. Hu, S. Fritschi and J.Lu. Emulsified oily wastewater treatment using a hybrid-modified resin and activated carbon system. *Sep. Purif. Technology*. 2008, **63**: 400–406.